Effects of Impurities on Fuel Cell Performance and Durability

J.G. Goodwin, Jr., Jack Zhang, K. Hongsirikarn, and Zhiming Liu

Clemson University

William Rhodes, Hector Colon-Mercado, and Scott Greenway

Savannah River National Lab

Peter Finamoore

John Deere, Advanced Energy Systems Division

Project ID#: FC29

Overview

- **Timeline**
  - Start: Feb. 15, 2007
  - Finish: Feb. 14, 2011
  - Completed: 25%

- **Budget**
  - Total Project Funding
    - DOE Share:
      - CU: $1,205,425
      - SRNL: $774,979
    - Cost Share:
      - CU: $295,101
      - John Deere: $193,745
  - Funding received in FY07
    - CU: $222,982
    - SRNL: $125,000
  - Funding for FY08
    - CU: $295,721
    - SRNL: $200,000

- **Barriers**
  - Fuel cells stacks do not maintain performance over the full useful lifetime of a vehicle.

- **Targets**
  - Test, analyze and characterize MEAs before, during and after operation
  - Develop electrocatalysts with reduced precious metal loading, increased activity, improved durability / stability and increased tolerance to air, fuel and system-derived impuritie
  - Develop sustainable MEA designs that meet all targets

- **Partners**
  - Clemson University
  - SRNL
  - John Deere

Objectives

- **Investigate in detail the effects of impurities in the hydrogen fuel and oxygen streams on the operation and durability of fuel cells.**
  - CO, CO_2, NH_3, H_2O, HCs (incl. C_2H_4, C_2H_6, H_2CO, HCOOH), O_2, inert gases (He, N_2, Ar), Cl_2, and H_2S.
- **Determine mechanisms of impurity effects.**
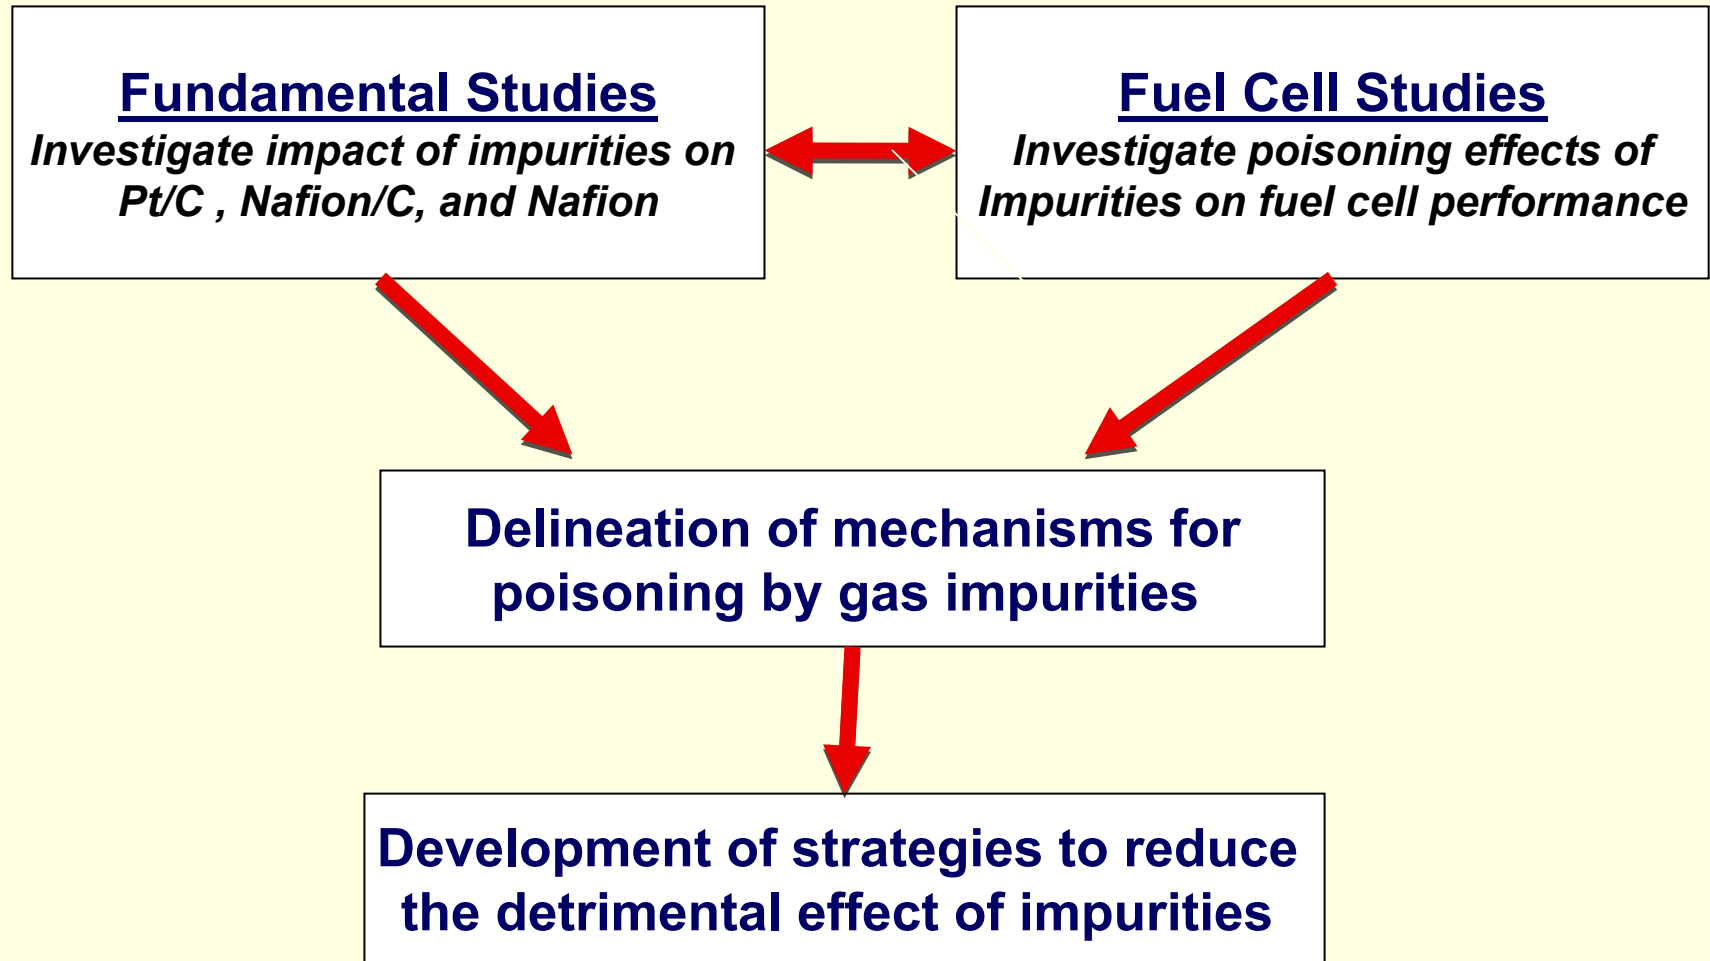- **Suggest ways to overcome impurity effects.**

Objectives – Year 1

- **Obtain and characterize components of MEA to be used (20% Pt/C, 30% Nafion/C, Nfn-Pt/C, Nafion membrane).**
- **Design and set up measurements of impact of impurities on MEA components.**
- **Install Fuel Cell Test Station.**
- **Calibrate FC Test Station measurements in "round robin" test of standard MEA with other DOE contractors.**
- **Start characterization of effects of CO and NH_3.**

Revised Milestones

Qtr	FY	Materials Acquisition /Prep./Modeling	Pt Study (Pt/C, Nafion/Pt/C)	Nafion Study (Nafion/C, Nafion/Pt/C and Nafion membrane)	PEMFC Performance Testing
1	2007	Materials purchase (Pt/C, PtRu/C, Nafion, gas mixtures)	training of student	training of student	Purchase of PEMFC
2	2007		Characterization of Pt/C	Characterization of Nafion/C	Installation of gas mix. sys.
3	2007		Constr. of H_2-D_2 and H_2-O_2 reaction system, start study of CO	Modif. of Nafion acidity test system. start study of NH_3	Design of test protocols
4	2008	Prep. of Nafion membranes for conductivity meas.	Integration of mass spec to reaction/ads. system, cont. CO study	Purchase of imped. meas. system, cont. study of NH_3	Finalizing test protocols, installation of FC Test Station, MEA preparation
5	2008	Prep. of Nafion membranes	**Effect of CO,**	**Effect of NH_3**	Round robin test of benchmark MEA, **Effect of CO**
6	2008		**Effect of CO, Effect of NH3**	**Effect of NH_3 Effect of CO**	**Effect of NH_3**
7	2008		**Effect of CO_2**	**Effect of CO_2**	**Effect of CO_2**
8	2009	**Development of poisoning model**	**Effect of Ethylene Effect of Ethane**	**Effect of Ethylene Effect of Ethane**	**Effect of Ethylene Effect of Ethane**
9	2009	**Go-No Go Decision**	**Go-No Go Decision**	**Go-No Go Decision**	**Go-No Go Decision**

CLEMSON UNIVERSITY

SRNL SAVANNAH RIVER NATIONAL LABORATORY

Approach

Fundamental Studies
Investigate impact of impurities on Pt/C , Nafion/C, and Nafion

Fuel Cell Studies
Investigate poisoning effects of Impurities on fuel cell performance

Delineation of mechanisms for poisoning by gas impurities

Development of strategies to reduce the detrimental effect of impurities

CLEMSON UNIVERSITY

SRNL
SAVANNAH RIVER NATIONAL LABORATORY

Experimental

Clemson

- **Phys. & Chem. Characterization**
    - **BET (Pt/C, Nafion, Naf-Pt/C)**
    - **XRD (Pt/C, Nafion, Naf-Pt/C)**
    - **SEM/TEM (Pt/C, Nafion, Naf-Pt/C)**
    - **EDS (Pt/C, Nafion, Naf-Pt/C)**
    - **FT-IR (Pt/C, Nafion, Naf-Pt/C)**
    - **H_2 Chemisorption (Pt/C, Naf-Pt/C)**
    - **Acid site titration (Nafion, Naf-Pt/C)**
    - **NH_3 ads. to meas. BA sites (Nafion, Naf-Pt/C)**
- *Reaction Characterization*
    - **H_2-D_2 (Pt/C, Naf-Pt/C)**
    - **H_2-O_2 (Pt/C, Naf-Pt/C)**
    - **Model BA-catalyzed reaction (Nafion, Naf-Pt/C)**
- *Conductivity Measurement*
    - **Impedance analysis (Nafion, Naf-Pt/C)**

SRNL

Impurity Mixture Generator (Up to 48 impurities at the time)

Gas Impurity Mixture Generator
Kin-Tek mixture generator
  Up to 48 mixed impurities
  Up to 500 sccm
FC Single Cell Test Station
*Arbin FCTS 200H*
  Max. Power: 200 W
  Max. Temp.: 130°C

Temperatures	**80° C**
Pressure	**2 bara ($P_a=P_c$)**
Humidity	**100 % RH anode, 50 % RH cathode**
Stoichiometry (A/C)	**H_2/Air = 1.1/2.5 @ 1000 mA/cm^2**
Loading	**Anode 0.1 mg Pt/cm^2 (20 wt% Pt-C)**
	Cathode 0.3 mg Pt/cm^2 (40 wt% Pt-C)
Electrolyte	**Nafion® 212**
Cell Area	**50 cm^2**
Current density	**1000 mA/cm^2**

Experimental: *Materials**

- **Anode: 20 wt% Pt/C (E-TEK)**
  - **Pt Particle Size: 22 Å (Co.)**
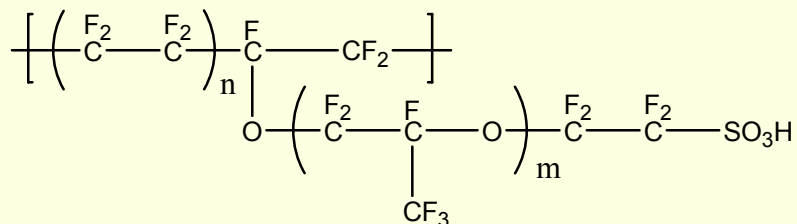 - **BET Surface Area: 112 m²/g (Co.)**

- **Cathode: 40 wt% Pt/C (E-TEK)**
  - ***Pt Particle Size: 29 Å (Co.)**
  - ***BET Surface Area: 100 m²/g (Co.)**

Fresh Pt/C
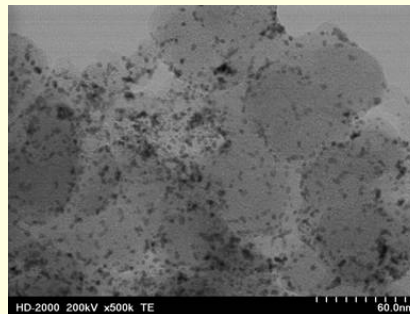
Element	Wt. %	Atom. %
C K	84.8	96.8
O K	2.5	2.1
S K	0.4	0.2
Pt M	12.4	0.8
Total	100	100

- **5 wt% Nafion EW 1100 Solution (Ion-Power)**

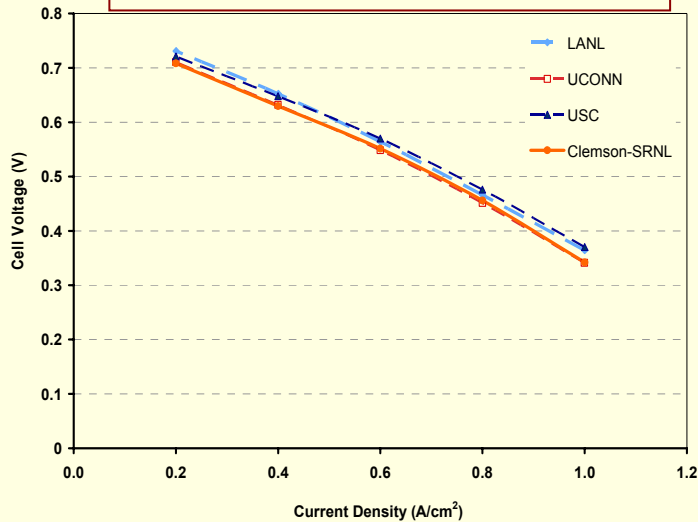**BET Surface Area:**
- C Support: 226 m²/g
- 20 wt% Pt/C: 112 m²/g
- 30 wt% Nafion/C: 59 m²/g
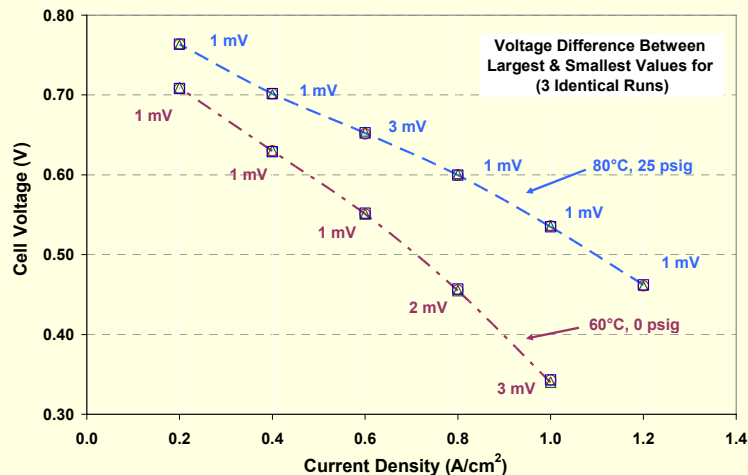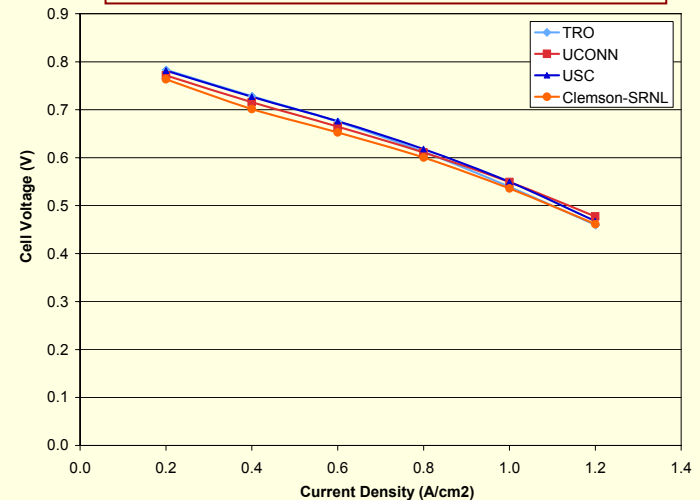- 30 wt% Nfn-Pt/C: 62 m²/g

Acid Site Density:
30 wt% Nafion/C: 270 µmol/g
30% Nfn-Pt/C: 227 µmol/g

- **Carbon Black Powder (XC-72R)**
  - **BET Surface Area: 250 m²/g (Co.)**

- **MEAs (E-TEK)**

- **Nafion ® 212 Membrane EW 1100 (Du Pont)**

* Commercial Products

USFCC Round Robin: *SRNL FC Results*

60°C, 0 psig, 100% RH

80°C, 25 psig, 100% RH

Voltage Difference Between Largest & Smallest Values for (3 Identical Runs)
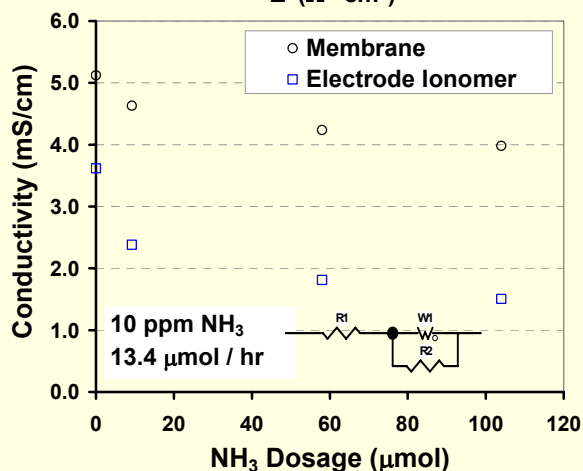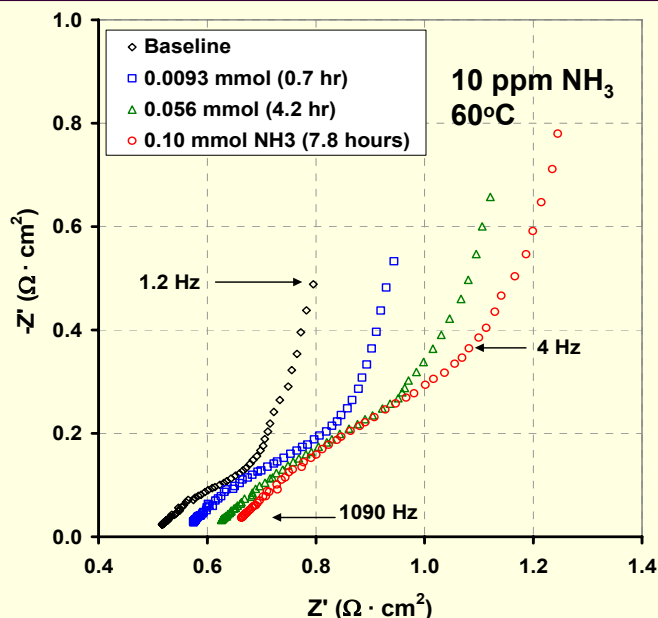
❑ **Excellent reproducibility** was found between labs and FC test stations.

❑ **Reproducibility** of the SRNL FC test station was excellent.
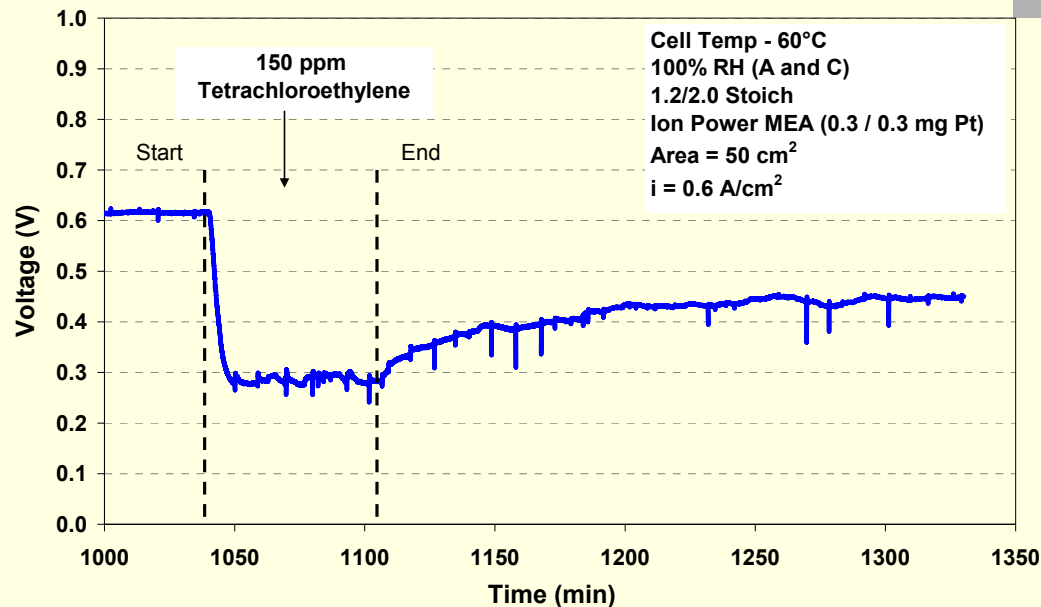
Electrochemical Impedance Spectroscopy (EIS):
10 ppm NH_3 Effect on Membrane & Ionomer @ 60°C

Baseline
0.0093 mmol (0.7 hr)
0.056 mmol (4.2 hr)
0.10 mmol NH3 (7.8 hours)

10 ppm NH_3
60°C

1.2 Hz
4 Hz
1090 Hz

$-Z'' (\Omega \cdot cm^2)$
$Z' (\Omega \cdot cm^2)$

Membrane
Electrode Ionomer

10 ppm NH_3
13.4 μmol / hr

Conductivity (mS/cm)
NH_3 Dosage (μmol)

- The __baseline__ run before poisoning is shown in black.

- Area corrected __membrane resistance__ is given by the high frequency intercept with the x-axis.

- The __ionomer resistance__ is proportional to the length of the "45°" line segment between 1090 Hz and ca. 4 Hz.

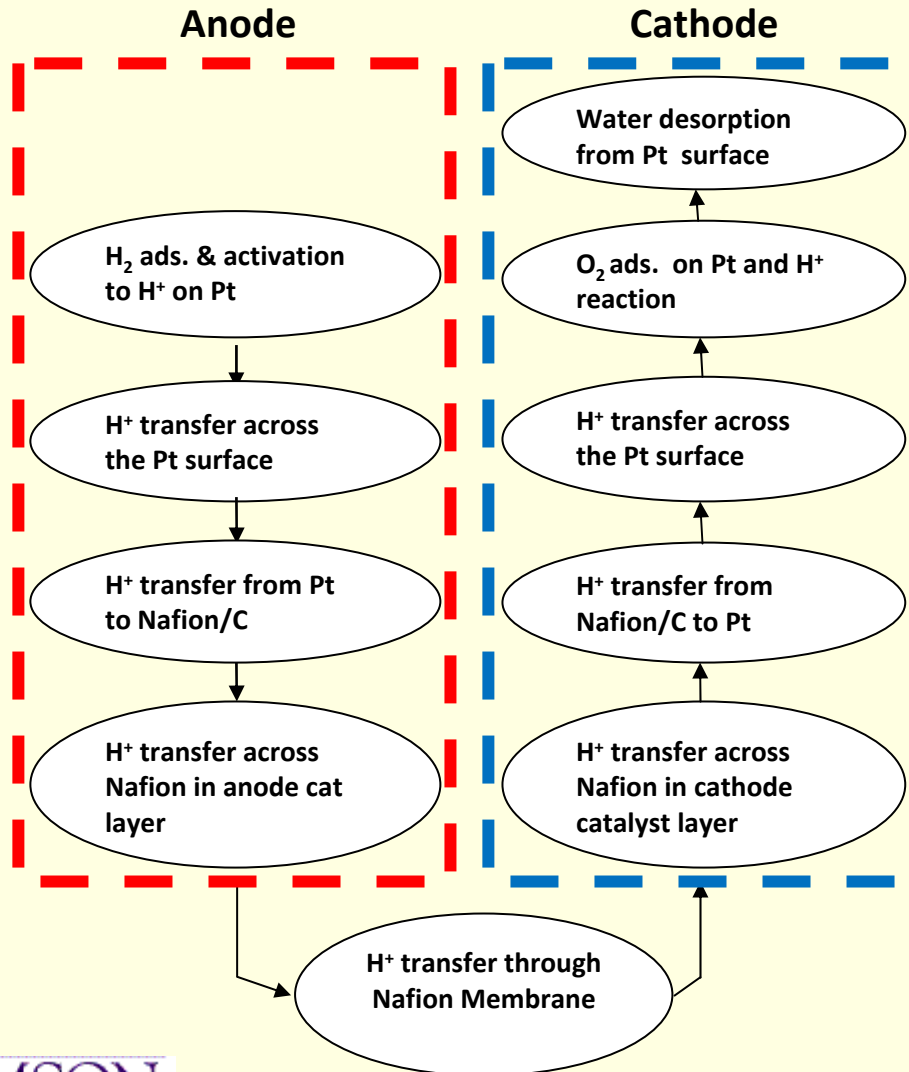- This analysis method shows that __both__ the membrane and electrode ionomer __resistances increase__ during NH_3 poisoning.

Ion Power MEA (0.3/0.3 mg Pt)
Working Electrode – 10 ppm NH_3 in Ar at 500 sccm (13.4 μmol / hr); 75% RH
Ref. / Counter Electrode - H_2 at 500 sccm ; 75% RH
Potential Bias (11 mV vs. OCV)
Perturbation (10 mV)
Inductance Correction (0.36 mH)

CLEMSON
UNIVERSITY

SRNL
SAVANNAH RIVER NATIONAL LABORATORY

PEMFC: Effect of Tetrachloroethylene @ 150 ppm

Graph: Voltage (V) vs Time (min). Labels: "150 ppm Tetrachloroethylene", "Start", "End". Conditions box: Cell Temp - 60°C, 100% RH (A and C), 1.2/2.0 Stoich, Ion Power MEA (0.3 / 0.3 mg Pt), Area = 50 cm^2, i = 0.6 A/cm^2

❑ **The impurities generator at SRNL can simulate many different individual contaminants or contaminant mixtures.**

❑ **As a preliminary checkout of the system, poisoning of a 50 cm^2 cell with <u>150 ppm of tetrachloroethylene</u> (dry), a representative chlorinated hydrocarbon typical of many degreasing agents, was carried out.**

❑ **Loss of more that <u>50% of the cell potential</u> resulted within a few minutes to give a new pseudo-steady-state operating potential. The cell was able to recover 50% of its loss when the impurity was stopped.**
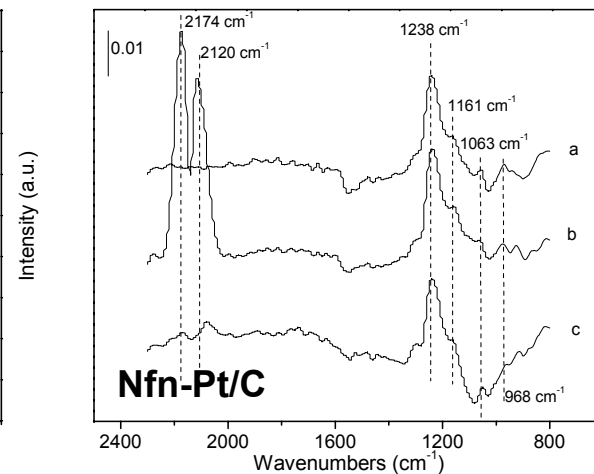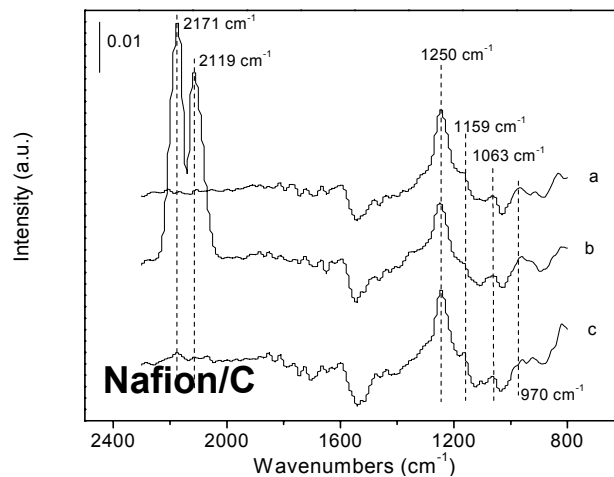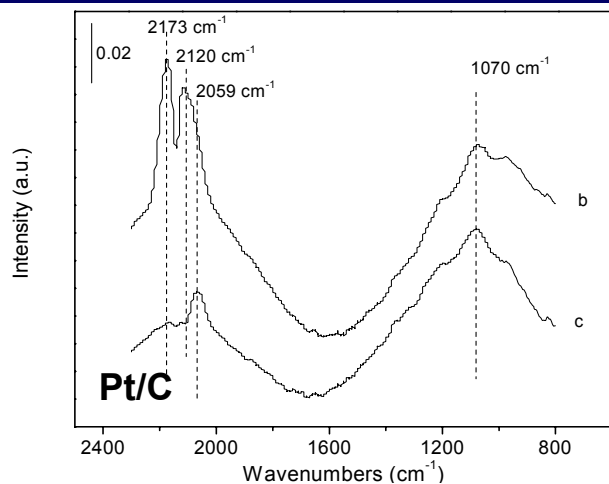
CLEMSON
UNIVERSITY

SRNL
SAVANNAH RIVER NATIONAL LABORATORY

Rate Steps during FC Operation

Anode

- H$_2$ ads. & activation to H$^+$ on Pt
- H$^+$ transfer across the Pt surface
- H$^+$ transfer from Pt to Nafion/C
- H$^+$ transfer across Nafion in anode cat layer

Cathode

- Water desorption from Pt surface
- O$_2$ ads. on Pt and H$^+$ reaction
- H$^+$ transfer across the Pt surface
- H$^+$ transfer from Nafion/C to Pt
- H$^+$ transfer across Nafion in cathode catalyst layer

H$^+$ transfer through Nafion Membrane

Use to model effect of poisons on fuel cell operation based on direct measurements.

DRIFTS spectra of CO on Nafion/C, Nfn-Pt/C, and 20% Pt/C:
a: fresh sample*; b: in flowing 4% CO in H₂; c: followed by H₂ purge at 80℃

IR band assignment

Wavenumber/cm⁻¹	Surface species
2171, 2119	gas phase CO
2059	linear CO
1250	CF_2 asymmetric stretching
1159	CF_2 symmetric stretching
1070	COH_x
1063	S-O symmetric stretching
970	C-O

- CO adsorbs on Pt/C as linear CO.
- CO does not adsorb on Nafion/C, which may explain the slight effect of CO on the activity of Nafion/C for esterification.

- The shift in wavenumber of CF_2 to lower frequency for Nfn-Pt/C indicates there is interaction between Pt and Nafion.
- CO adsorbs less and more weakly on Nfn-Pt/C, perhaps due to this interaction.
- COH_x species appear to be formed on Pt/C in the presence of CO and H₂.
- CO and COH_x species block Pt sites required for H₂ adsorption, resulting in lower performance of the PEMFC.

* The fresh samples were treated in H₂ at 80 ℃ for 3 hours prior to IR.

DRIFTS spectra of NH₃ on Nafion/C:

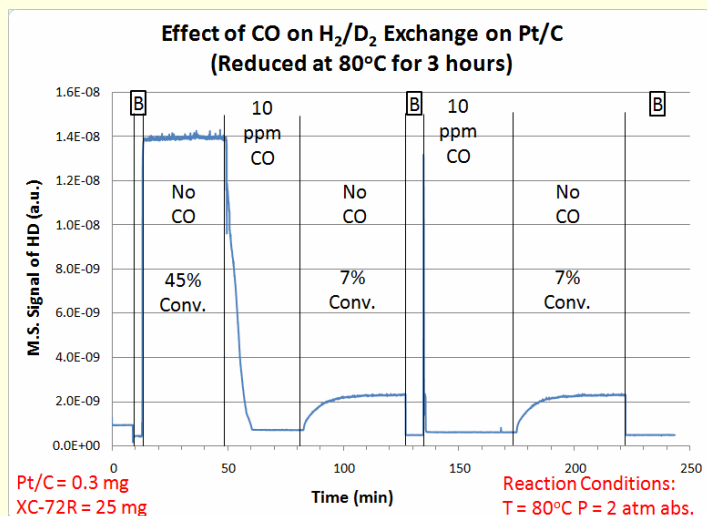## a: fresh Nafion/C; b: flowing 750 NH₃ in H₂; c: after He purge at 80℃ .
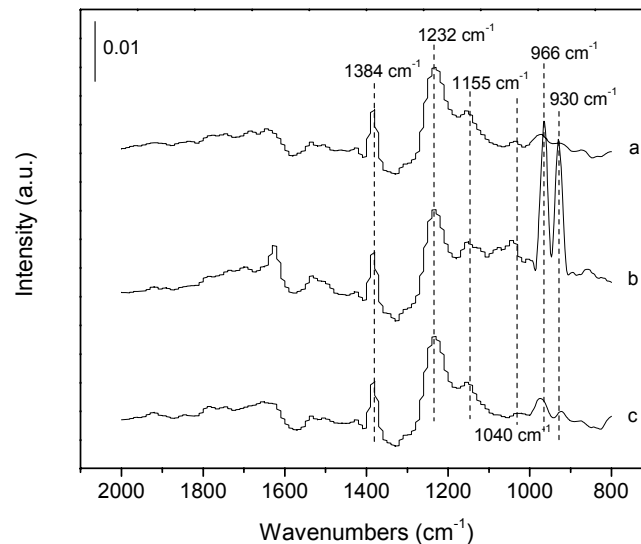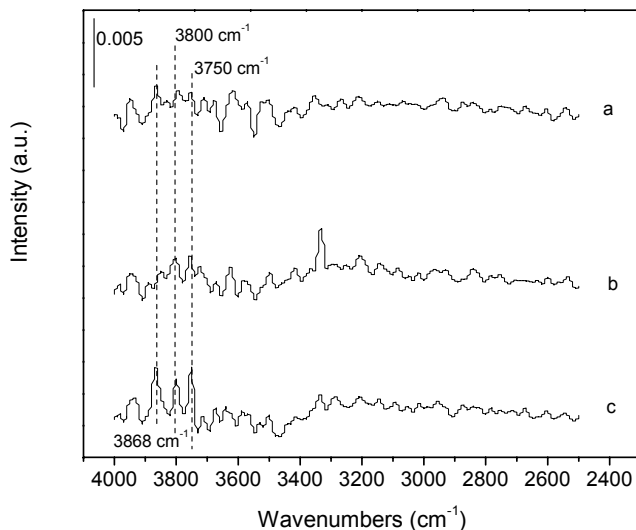
IR band assignment

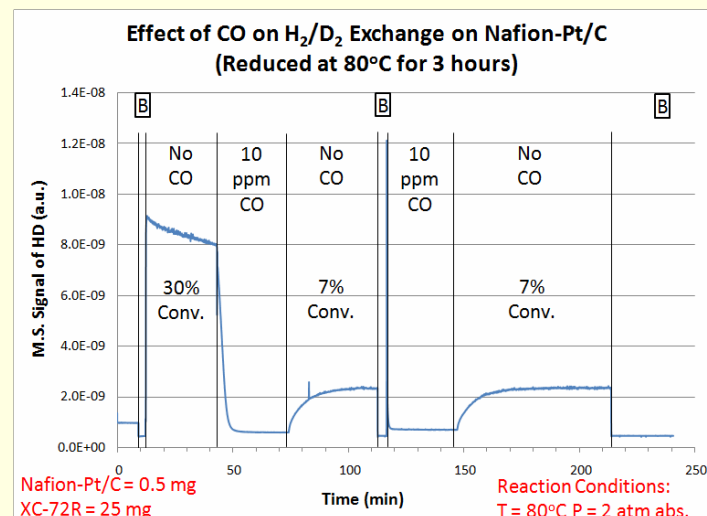| Wavenumber/cm^{-1}	Surface species
3868, 3800, 3750	NH_4^+
1384	CF_2 asymmetric stretching
1232	CF_2 asymmetric stretching
1155	CF_2 symmetric stretching
1040	S-O symmetric stretching
966, 930	gas phase NH_3

❑ **Peaks assigned to NH_4^+ can be observed, indicating that NH_3 absorbed on the Bronsted acid sites of Nafion forming NH_4^+.**

❑ **The formation of NH_4^+ reduces the proton conductivities of the Nafion membrane and the anode catalyst ionomer layer.**
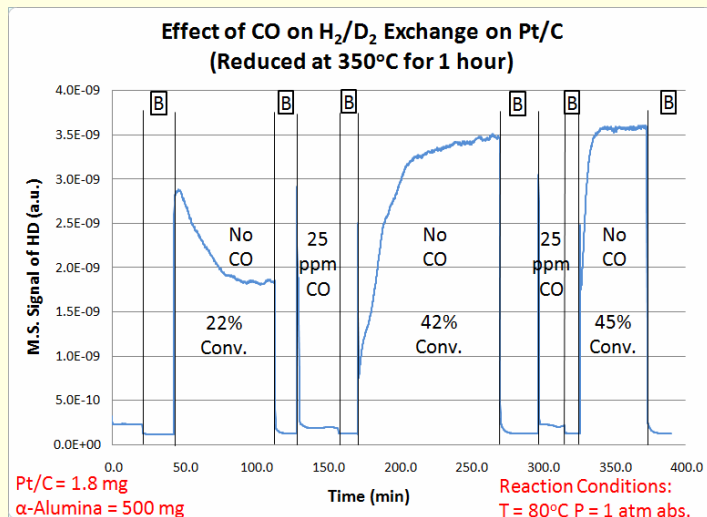
Effect of 10 ppm of CO on H₂ Activation

Pt/C

Effect of CO on H₂/D₂ Exchange on Pt/C
(Reduced at 80°C for 3 hours)

No CO — 45% Conv. | 10 ppm CO | No CO — 7% Conv. | 10 ppm CO | No CO — 7% Conv.

Pt/C = 0.3 mg
XC-72R = 25 mg

Reaction Conditions:
T = 80°C P = 2 atm abs.

Nfn-Pt/C

Effect of CO on H₂/D₂ Exchange on Nafion-Pt/C
(Reduced at 80°C for 3 hours)

No CO — 30% Conv. | 10 ppm CO | No CO — 7% Conv. | 10 ppm CO | No CO — 7% Conv.

Nafion-Pt/C = 0.5 mg
XC-72R = 25 mg
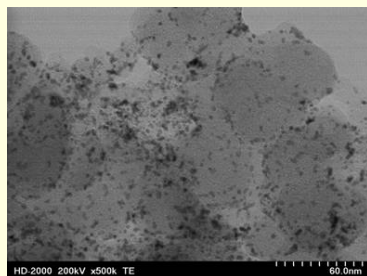
Reaction Conditions:
T = 80°C P = 2 atm abs.

- ❑ **Pt/C is very active for H₂ dissoc. (equilibrium reached with only 0.3 mg of catalyst).**
- ❑ **Pt/C is effectively poisoned in 10 min, suggesting that practically every CO adsorbs.**
- ❑ **Nafion-Pt interactions cause H₂ dissociation to be somewhat inhibited on Nfn-Pt/C.**
- ❑ **Nafion-Pt interactions may be due to interactions with sulfonic acid groups/CF₂.**
- ❑ **Presence of CO, even at 10 ppm, stops H₂ activation.**
- ❑ **Poisoning effect is partially reversible at 80°C within 20 min, but most CO strongly bound.**

20 wt% Pt/C = 677 µmol Pt$_s$/g-cat. For 0.3 mg Pt/C = 0.20 µmol Pt
Flow of 10 ppm CO = 0.041 µmol CO/min

Effect of 25 ppm of CO on H_2 Activation

Effect of CO on H_2/D_2 Exchange on Pt/C
(Reduced at 350°C for 1 hour)

M.S. Signal of HD (a.u.) vs Time (min)

No CO — 22% Conv.
25 ppm CO
No CO — 42% Conv.
25 ppm CO
No CO — 45% Conv.

Pt/C = 1.8 mg
α-Alumina = 500 mg
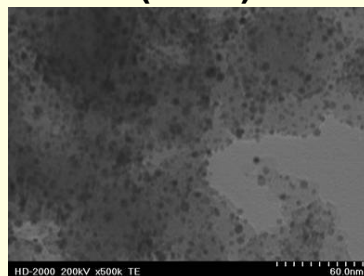
Reaction Conditions:
T = 80°C P = 1 atm abs.
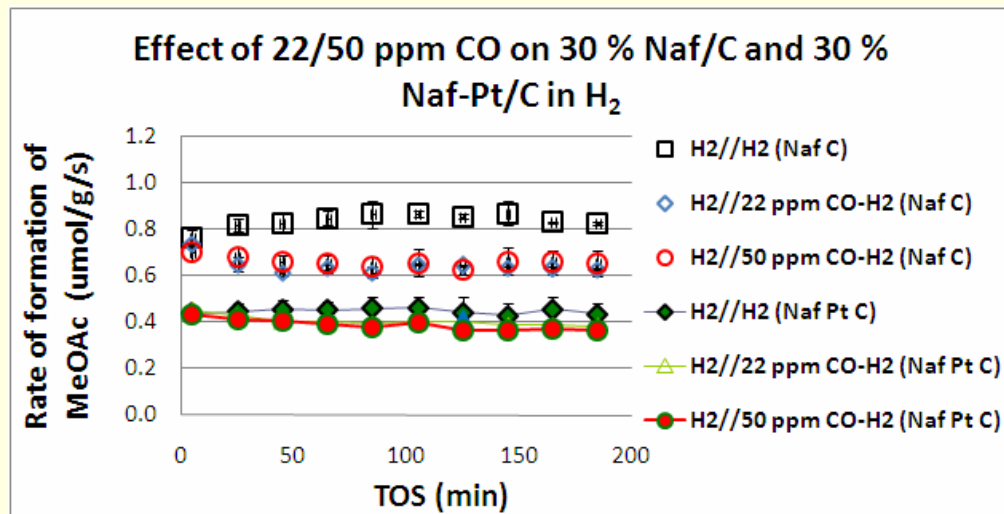
Fresh Pt/C

d_{Pt} = 2.9 nm

Red. (350°) Pt/C

d_{Pt} = 4.8 nm

- ❑ **If Pt/C is <u>reduced at 350°C</u>, the Pt particles sinter and the activity is less since the amount of exposed Pt surface atoms is less.**
- ❑ **The Pt particle diameters increase from 2.9 to ca. 4.8 nm.**
- ❑ **25 ppm CO also results in total loss of activity.**
- ❑ **However, for these larger particles of Pt,**
  - ❑ **there is a total recovery of activity within 10-25 min. (no irrev. ads. CO).**
  - ❑ **increased H_2 activation is possibly due to Pt surface restructuring.**

CLEMSON UNIVERSITY

SRNL SAVANNAH RIVER NATIONAL LABORATORY

Effect of CO on Nafion/C and Nfn-Pt/C

Effect of 22/50 ppm CO on 30 % Naf/C and 30 % Naf-Pt/C in H_2

Legend:
- □ H2//H2 (Naf C)
- ◇ H2//22 ppm CO-H2 (Naf C)
- ○ H2//50 ppm CO-H2 (Naf C)
- ◆ H2//H2 (Naf Pt C)
- △ H2//22 ppm CO-H2 (Naf Pt C)
- ● H2//50 ppm CO-H2 (Naf Pt C)

X-axis: TOS (min), Y-axis: Rate of formation of MeOAc (umol/g/s)

Surface sites of Pt/C*
- 20% Pt/C = 677 µmol H/g
*Calc. from H_2 chemisorption
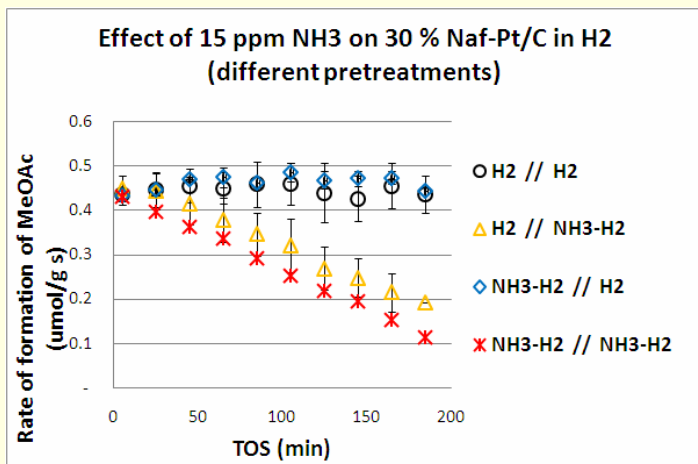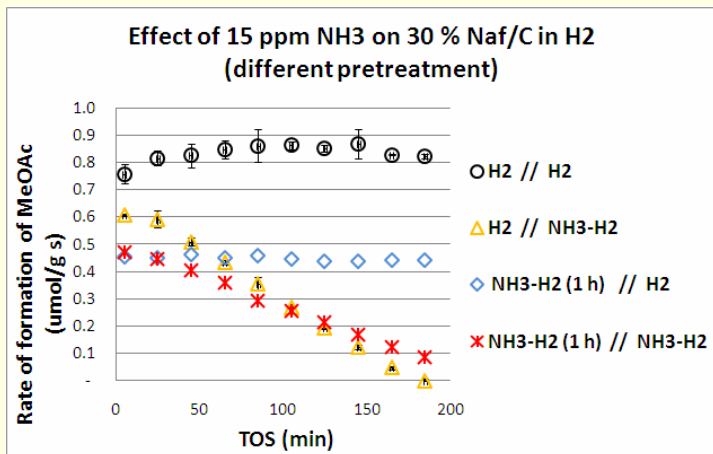
Proton site density*
- 30% Nafion/C = 270 µmol/g
- 30% Nfn-Pt/C = 227 µmol/g
*Based on S analysis

Esterification of HAc: Pres. = 1 atm (abs.),T = 80ºC, P_{MeOH} and P_{HAc} = 0.01 atm, Tot. flow rate = 100 sccm

- ❑ **The activity of 30% Nafion/C is greater than that of 30% Nfn-Pt/C. Pt appears to catalyze removal of some of the S when Nafion added to Pt/C [S content decrease while F content remains constant.**

- ❑ **The interaction of Pt with sulfonic acid groups/CF_2 may decrease the strength/number of acid sites in Nafion.**

- ❑ **CO has a small effect on the acidity.**

- ❑ **Even 22 ppm of CO causes the maximum effect.**

CLEMSON UNIVERSITY

SRNL SAVANNAH RIVER NATIONAL LABORATORY

Effect of NH₃ on Nafion/C and Nfn-Pt/C

Effect of 15 ppm NH3 on 30 % Naf/C in H2 (different pretreatment)

- ○ H2 // H2
- △ H2 // NH3-H2
- ◇ NH3-H2 (1 h) // H2
- ✕ NH3-H2 (1 h) // NH3-H2

X-axis: TOS (min), Y-axis: Rate of formation of MeOAc (umol/g s)

Effect of 15 ppm NH3 on 30 % Naf-Pt/C in H2 (different pretreatments)

- ○ H2 // H2
- △ H2 // NH3-H2
- ◇ NH3-H2 // H2
- ✕ NH3-H2 // NH3-H2

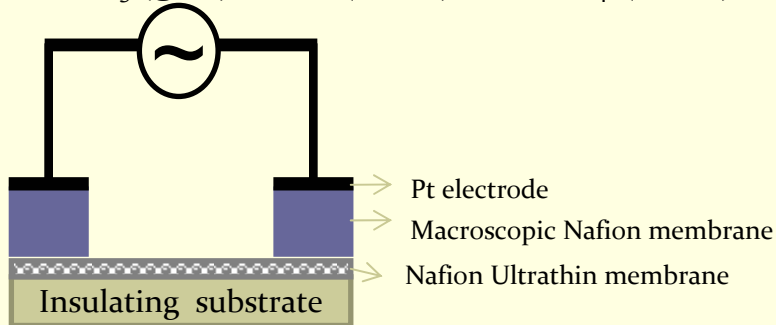X-axis: TOS (min), Y-axis: Rate of formation of MeOAc (umol/g s)

- ❑ **The poisoning effect of NH₃ is cumulative and even at 15 ppm appears to be irreversible.**

- ❑ **The effect of NH₃ on the Brønsted acid sites on Nafion/C is more than that on Nfn-Pt/C.**

- ❑ **Pt may decompose NH₃ resulting in less poisoning of Nafion in Nfn-Pt/C.**

- ❑ **From NH₃ pulse chemisorption, it was found that NH₃ can adsorb on Pt/C leading to competitive adsorption of NH₃ on Pt/C and the sulfonic acid ions of Nafion.**

Esterification of HAc: Pres. = 1 atm (abs.), T = 80 C, P_{MeOH} and P_{HAc} = 0.01 atm, Tot. flow rate = 100 sccm

Proton site density*
- 30 % Naf/C   = 270 µmol/g
- 30 % Naf-Pt/C = 227 µmol/g

CLEMSON UNIVERSITY

* Calculated by S elemental analysis

SRNL — SAVANNAH RIVER NATIONAL LABORATORY

Impedance Measurement: *10 ppm NH₃ on Nafion 212*

$$NH_3(gas) + H^+(mem) \leftrightarrow NH_4^+(mem)$$

Pt electrode
Macroscopic Nafion membrane
Nafion Ultrathin membrane
Insulating substrate

Conditions: T = 60°C, RH = 50%, 125 ppm NH₃ in He

■ **Electrochemical cell designed to test ionic conductivity in the membrane**

■ **Electrochemical Impedance Spectroscopy (EIS) is being used to test Nafion membrane and Nafion/C properties with poisoning**

Conductivity of NRE 212 in the presence of 10 ppm NH₃/He at 60° C, 50% RH
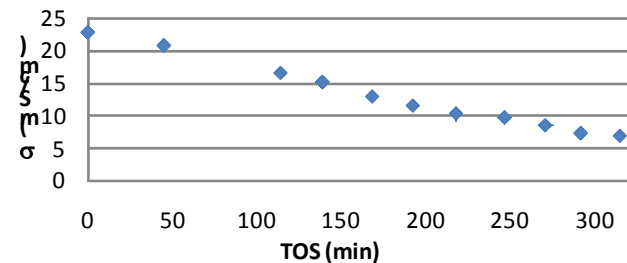
σ (mS/m)

TOS (min)

Conductivity of NRE 212 in the presence of 10 ppm NH₃/He at 60° C, 50% RH

σ (mS/m)

Amount of NH₃ fed (μmol)
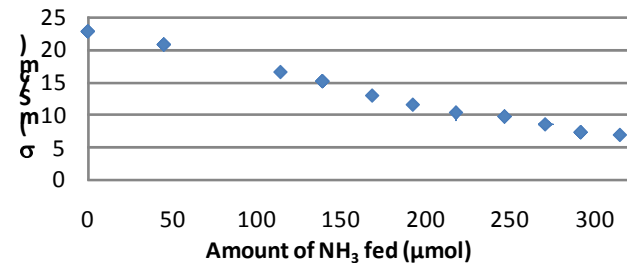
❑ σ (H⁺ form) = 22.7 mS/cm
❑ σ (H⁺ form from Springer model) = 22.3 mS/cm*
❑ σ (NH₄⁺ form) = 7 mS/cm
❑ σ of H⁺ form Nafion® is ca. 3 times higher than NH₄⁺ form which is in agreement with the value that Uribe et. al reported (3.8–4.2 times).**

CLEMSON
UNIVERSITY

SRNL
SAVANNAH RIVER NATIONAL LABORATORY

*   T.E. Springer, J. Electrochem. Soc., 138, 2334 (1991).
** F.A. Uribe, T.A. Zawodzinski Jr., S. Gottesfeld, J. Electrochem. Soc. 149 (2002) A293.

Fundamental Modeling Collaboration:
Clemson /SRNL/GreenWay Energy

- **Review Contaminant Model Literature**
  - Survey PEM literature to understand contaminant models.
  - Identify most relevant poisoning mechanism for CO and NH_3.
- **Develop First Principles Kinetic & Rate Expressions**
  - Create model as a tool for understanding *ex-situ* data.
  - Relate *ex-situ* and *in-situ* results.
- **Predict Results for Fuel Cell Testing**
  - Use comprehensive contaminant model to predict cell test results.
- **Program Model Code**
  - Give researchers direct access to model predictions in an easy to use format such as Maple or Matlab.

GreenWayEnergy™
POWERFUL EXPERTS

CLEMSON
UNIVERSITY

UNIVERSITY OF
SOUTH
CAROLINA

SRNL
SAVANNAH RIVER NATIONAL LABORATORY

Future Work (FY08-FY09)

- **Activities**
  - **Complete studies of the effects of CO, NH_3, CO_2, ethane, and ethylene on fundamental processes and fuel cell performance.**
  - **Develop model for incorporating fundamental results to predict FC behavior.**
  - **Determine how well the measurement of effects on FC components predict FC performance.**
- **Upcoming Milestones**
  - **Complete fundamental studies of effects of CO, NH_3, CO_2, ethane and ethylene on Pt/C, Nafion/C, and Nafion membrane.**
  - **Complete FC runs of effects of CO, NH_3, CO_2, ethane and ethylene on FC performance.**
- **Decision Points**
  - **Go-No Go decision at end of 2nd quarter FY 2009**

Summary

- Project started in Feb. 2007.
- MEA components acquired and characterized March-Oct. 2007.
- FC test station installed & operational in Nov. 2007
- Fundamental studies of CO indicated how Pt surface covered with CO prevents completely H_2 activation even at 10 ppm.
- Larger Pt particles appear to adsorb CO more reversibly with some surface restructuring likely.
- Pt interacts with Nafion in Nfn-Pt/C and appears to cause some decrease in S content.
- NH_3 at 10 ppm accumulates on the proton sites of the Nafion membrane decreasing proton conductivity >3X.
- Pt helps to protect Nafion from NH_3, but decomposed products may interact with organics to deactivate proton sites.
- Round Robin FC MEA test completed Jan. 2008 with excellent match.
- FC tests carried out for NH_3 and tetrachloroethylene.
- FC used to perform Electrochemical Impedance Spectroscopy to analyze conductivities, membrane performance and catalyst performance.

CLEMSON UNIVERSITY

SRNL
SAVANNAH RIVER NATIONAL LABORATORY